



Pavement Cracking

Mechanisms, Modeling, Detection, Testing, and Case Histories

Editors

Imad L. Al-Qadi, Tom Scarpas & Andreas Loizos

 **CRC Press**
Taylor & Francis Group
A BALKEMA BOOK

PROCEEDINGS OF THE 6TH RILEM INTERNATIONAL CONFERENCE ON CRACKING
IN PAVEMENTS, CHICAGO, USA, 16–18 JUNE 2008

Pavement Cracking

*Mechanisms, Modeling, Detection,
Testing and Case Histories*

Editors

Imad L. Al-Qadi

University of Illinois at Urbana Champaign, Urbana, Illinois, USA

Tom Scarpas

Delft University of Technology, Delft, The Netherlands

Andreas Loizos

National Technical University of Athens, Athens, Greece



CRC Press is an imprint of the
Taylor & Francis Group, an **informa** business

A BALKEMA BOOK

CRC Press/Balkema is an imprint of the Taylor & Francis Group, an informa business

© 2008 Taylor & Francis Group, London, UK

Typeset by Charon Tec Ltd (A Macmillan Company), Chennai, India
Printed and bound in the USA by Edwards Brothers, Inc, Lillington, NC.

All rights reserved. No part of this publication or the information contained herein may be reproduced, stored in a retrieval system, or transmitted in any form or by any means, electronic, mechanical, by photocopying, recording or otherwise, without written prior permission from the publishers.

Although all care is taken to ensure integrity and the quality of this publication and the information herein, no responsibility is assumed by the publishers nor the author for any damage to the property or persons as a result of operation or use of this publication and/or the information contained herein.

Published by: CRC Press/Balkema
P.O. Box 447, 2300 AK Leiden, The Netherlands
e-mail: Pub.NL@taylorandfrancis.com
www.crcpress.com – www.taylorandfrancis.co.uk – www.balkema.nl

ISBN 13: 978-0-415-47575-4 (Hbk + CD-rom)

Table of contents

Preface	xiii
Organization	xv
<i>1. Accelerated pavement testing to assess pavement structure, interface bonding and reflective cracking</i>	
Evaluation of reflective cracking performance of asphalt mixes with asphalt rubber binder using HVS tests and non-local continuum damage mechanics <i>R.Z. Wu & J.T. Harvey</i>	3
The LCPC's ALT facility contribution to pavement cracking knowledge <i>P. Hornyh, J.P. Kerzreho, A. Chabot, D. Bodin, J.M. Balay & L. Deloffre</i>	13
Pavement strength measured by full scale test <i>E.H. Guo, L. Ricalde & F. Petch</i>	25
Fatigue cracking characteristics of accelerated testing pavements with modified binders <i>X. Qi, N. Gibson & J. Youtcheff</i>	35
An overview of an accelerated pavement testing experiment to assess the use of modified binders to limit reflective cracking in thin asphalt concrete overlays <i>D. Jones, J.T. Harvey & T. Bressette</i>	45
Accelerated pavement cracking testing: experimental and finite element analysis <i>S.A. Pérez, J.M. Balay, P. Tamagny, A. Chabot, Ch. Petit, A. Millien & L. Wendling</i>	55
<i>2. Analytical and experimental investigations of concrete joints</i>	
Influence of the coefficient of thermal expansion on the cracking of jointed concrete pavements <i>E. Kohler & V. Kannekanti</i>	69
An analytical approach to computing joint opening in concrete pavements <i>J.R. Roesler & D. Wang</i>	79
Experimental behavior of construction joints in FRC pavements <i>L. Cominoli, A. Meda & G.A. Plizzari</i>	89
Induction of joints in concrete pavements <i>J.R. Vázquez</i>	99
Numerical assessment of saw-cutting: The influence on stress development and cracking <i>K. Raoufi, J. Weiss & T. Nantung</i>	109
Moisture warping in slabs on grade <i>Y. Wei, W. Hansen & E. Schlagen</i>	119

<i>3. Performance of concrete pavements and white topping</i>	
Cracking in concrete pavements – an interaction of various influences <i>R. Breitenbücher & C. Sievering</i>	127
Consequences of fracture mechanics for size effect, crack spacing and crack width in concrete pavements <i>C.G. Hoover & Z.P. Bazant</i>	137
Assessment and mitigation of early-age cracking in concrete pavements due to restrained movement <i>S.S. Tyson, S.D. Tayabji & H.T. Yu</i>	145
The effect of different axle configurations on the fatigue life of plain cement concrete <i>K. Chatti, N.A. Brake, H. Salama & S.W. Haider</i>	155
Evaluation of factors influencing distress development in ultra-thin whitetopping <i>S.A. Newbolds & J. Olek</i>	167
Restrained shrinkage cracking of fiber-reinforced self-consolidating concrete <i>S.H. Kwon, R.P. Ferron, Y. Akkaya & S.P. Shah</i>	179
<i>4. Cracking in semi-rigid and stabilized-base pavements</i>	
Prediction of fatigue cracking in cement treated base courses <i>A.A.A. Molenaar & B. Pu</i>	189
Cracking response and service life prediction of flexible and semi-rigid road pavements implementing M-E PDG 2002 code <i>M. la Agostinacchio, D. Ciampa & S. Olita</i>	201
A prediction procedure of reflective cracking growth life for cement stabilized base asphalt pavement <i>F.-J. Ni & Q. Li</i>	211
Cracking survey on freeways using asphalt pavement with semi-rigid base in Jiangsu <i>J. Yang, H. Lu & Y. Yang</i>	221
Asphalt sand stress absorbing interlayer used in asphalt pavement with semi-rigid base <i>J. Yang, P. Dai, B. Yu & Y. Yang</i>	229
Effectiveness of slab stabilization in mitigating reflective cracking in HMA overlays: A case-history <i>F.G. Praticò & M. Losa</i>	239
Fatigue performance of self cementing base courses <i>A.A.A. Molenaar</i>	251
<i>5. Fatigue cracking and damage characterization of HMA</i>	
A five point bending test for asphalt cracking on steel plates <i>A. Houel & L. Arnaud</i>	261

FE evaluation of 4-point bending test for fatigue cracking assessment <i>M. Coni, S. Portas, R. Isola & J.R.M. Oliveira</i>	271
Investigation of cracking in bituminous mixtures with a 4 points bending test <i>M.L. Nguyen, C. Sauzeat, H. Di Benedetto & L. Wendling</i>	283
A micromechanics-based computational model and testing protocols to characterize damage-dependent mechanical responses of asphalt mixtures in flexible pavements <i>Y.-R. Kim, F.A.C. de Freitas & D.H. Allen</i>	295
Use of pseudostress and pseudostrain concepts for characterization of asphalt fatigue tests <i>M.E. Kutay, N.H. Gibson & J. Youtcheff</i>	305
Viscoelastic continuum damage model based finite element analysis of fatigue cracking <i>C. Baek, B.S. Underwood, V. Subramanian, M.N. Guddati, Y.R. Kim & K. Lee</i>	315
 <i>6. Top-down cracking in flexible pavements</i>	
Finite element analysis of top-down cracking in semi-rigid pavement structure <i>P. Wang, X.-M. Huang, Q.-F. Li & Z.-T. Yang</i>	327
Investigation of fatigue cracking: Bottom-up or top-down <i>X. Hu, S. Hu, L. Sun & L.F. Walubita</i>	333
Strength theory, a better explanation for top-down cracking in asphalt pavement <i>L. Jia, L. Sun, X. Hu & X. Hu</i>	345
Modeling shear properties of airport asphalt mixes using different test methods <i>A. El-Desouky, A. Mostafa, S. Easa & A.O. Abd El Halim</i>	357
 <i>7. Low temperature cracking in HMA</i>	
Integration of laboratory testing, field performance data and numerical simulations for the study of low-temperature cracking <i>E.V. Dave, A.F. Braham, W.G. Buttlar, G.H. Paulino & A. Zofka</i>	369
Thermal cracking prediction using artificial neural network <i>M. Zeghal</i>	379
Effect of aggregate grading on low temperature cracking resistance in asphalt mixtures base on mathematical statistic <i>Y.-Q. Tan, H.-N. Xu, Z.-J. Dong & W.-Q. Gong</i>	387
Discrete element modelling of low temperature monotonic compression tests in an idealised asphalt mixture <i>J. Wu, A. Collop & G. McDowell</i>	395
Investigation of low temperature cracking in asphalt mixtures using TSRST <i>R. Velásquez, M. Turos, M. Marasteanu, N. Gibson & T. Clyne</i>	405

<i>8. Binder and HMA laboratory characterization for cracking potential</i>	
Measurement and effective evaluation of crack growth in asphalt mixtures <i>H.A. Khalid & I. Artamendi</i>	417
Evaluation of fracture properties of hot mix asphalt <i>L.N. Mohammad, M.D. Kabir & S. Saadeh</i>	427
Crack propagation performance evaluation of asphaltic mixes using a new procedure based on cyclic semi-circular bending tests <i>R.C. van Rooijen & A.H. de Bondt</i>	437
A new laboratory test for reflective cracking in mode I and/or mode II <i>D. Perraton, G. Guissi, P. Pierre & G. Doré</i>	447
New procedure to evaluate fatigue of bituminous mastics using an annular shear rheometer prototype <i>B. Delaporte, J. Van Rompu, H. Di Benedetto, P. Chaverot & G. Gauthier</i>	457
Thermo-volumetric properties of asphalt binders and mixtures <i>J.O. Ojo, D. Fratta, H.U. Bahia, C. Daranga & M. Marasteanu</i>	469
Low temperature behavior of very hard bituminous binder material for road applications <i>R.N. Khedoe, A.A.A. Molenaar & M.F.C. v.d. Ven</i>	481
Comparison of the modulus of high-modulus asphalt mixtures – experimental determination and calculation <i>F. Vervaecke, J. Maeck & A. Vanelstraete</i>	491
Acoustic emission in asphalt mixture IDT creep and strength tests <i>X. Li, M.O. Marasteanu & J.F. Labuz</i>	501
The effects of different waveforms and rest period in cyclic loading on the fatigue behavior of the asphalt mixtures <i>K. Kogo & K. Himeno</i>	509
Evaluation of cracking in recycled pavements with foamed asphalt and cement stabilization <i>A. Loizos & V. Papavasiliou</i>	519
The effects of cracking type and location on the choice of asphalt pavement recycling method <i>S.W. Haider, G.Y. Baladi, T. Akram & A. Hussain</i>	529
Cracks in porous European mixes: A theoretical and experimental study <i>F.G. Praticò, R. Ammendola & A. Moro</i>	539
<i>9. Pavement modeling-response, crack analysis, and damage prediction</i>	
Reflective cracking behavior for traffic and temperature effects <i>M.J.C. Minhoto, J.C. Pais & P.A.A. Pereira</i>	551
Mechanism of overlay reinforcement to retard reflective cracking under moving vehicular loading <i>J. Baek & I.L. Al-Qadi</i>	563
Virtual testing procedure for cracking performance prediction of HMA <i>Z. Feng, P. Zhang, M.N. Guddati, Y.R. Kim & D.N. Little</i>	575

Structural impact and dynamics response in brittle materials <i>M. Buonsanti, G. Leonardi & F. Scopelliti</i>	587
Multiscale computational modeling for predicting evolution of damage in asphaltic pavements <i>R.F. Soares, Y.-R. Kim & D.H. Allen</i>	599
Finite element modeling of fatigue shear tests: Contribution to pavement lifetime design under traffic loading <i>F. Bouhas, A. Millien & C. Petit</i>	609
Shift factor model evaluations using tested data from PMA at low temperatures and data reductions methods for IDT and HT-BBR testing <i>B.-Q. Bai</i>	617
An experimental investigation of the fracture mechanics of bitumen and asphalt <i>O. Portillo & D. Cebon</i>	627
Using semi-analytical finite element method to evaluate stress intensity factors in pavement structure <i>S. Hu, X. Hu & F. Zhou</i>	637
 <i>10. Pavement interface testing and modeling</i>	
Interface fatigue cracking in multilayered pavements: Experimental analysis <i>M. Diakhaté, Ch. Petit, A. Millien, A. Phelipot-Mardelé, B. Pouteau & H. Goacolou</i>	649
A fracture-based constitutive model for pavement interface characterization <i>H. Ozer, I.L. Al-Qadi & Z. Leng</i>	661
FABAC accelerated loading test of bond between cement overlay and asphalt layers <i>A. Chabot, J.M. Balay, B. Pouteau & F. de Larrard</i>	671
Low temperature cracking in asphalt overlays bonded to rigid pavements <i>H.M. Yin, W.G. Buttlar & G.H. Paulino</i>	683
 <i>11. Interlayer system effectiveness in reducing reflective cracking in pavements</i>	
Techniques to mitigate reflective cracking in asphalt overlay <i>H. Wen & W. Shitangkoon</i>	695
Proper installation of paving fabric interlayers when placed prior to chip sealing <i>L. Davis & J. Dendurant</i>	703
The use of geogrids to retard reflective cracking on airport runways, taxiways and aprons <i>J. Penman & K.D. Hook</i>	713
Evaluation of fiber reinforced bituminous interlayers for pavement preservation <i>C. Palacios, G.R. Chehab, F. Chaignon & M. Thompson</i>	721

Installation and performance of a fiberglass geogrid interlayer on the NCAT Pavement Test Track <i>R.B. Powell</i>	731
Evaluation of reflective cracking performance of AC mixes with asphalt rubber binder using HVS tests and recursive mechanistic-empirical analysis <i>P. Ullidtz, J. Harvey, D. Jones & B.-W. Tsai</i>	741
Fatigue investigations of asphalt concrete beams reinforced with geosynthetics interlayer <i>P. Zieliński</i>	751
On site validation and long term performance of anti-cracking interfaces <i>F. Vervaecke, J. Maeck & A. Vanelstraete</i>	761
Laboratory study of geogrid reinforcement in Portland cement concrete <i>X. Tang, G.R. Chehab & S. Kim</i>	769
Performance and service life prediction of crack preventative joint systems <i>C. Recknagel, S. Pirskawetz & F. Lüddecke</i>	779
Anti-reflective cracking solutions for asphalt overlays: 8 years performance monitoring <i>M.L. Antunes, S. Fontul & A.M. Pinelo</i>	791
 <i>12. Field investigation of pavement cracking</i>	
Development of reflective cracking index to determine the effectiveness and service life of strip interlayer systems <i>I.L. Al-Qadi, J. Baek & W.G. Buttlar</i>	801
The use of digital image correlation for accurate determination of fracture energy density in Hot Mix Asphalt (HMA) <i>B. Birgisson, A. Montepara, E. Romeo, R. Roncella, G. Tebaldi & R. Roque</i>	811
Mitigating reflective cracking under Nevada's conditions <i>N.E. Morian, E.Y. Hajj & P.E. Sebaaly</i>	821
A practical methodology for the performance-based selection of bituminous mixtures for concrete overlays <i>T. Bennert & A. Maher</i>	833
Case history on surface initiated cracks on urban thoroughfare pavements <i>L.A. Cooley, Jr., I.L. Howard, G. Baumgardner & M. Ross</i>	843
Investigation of transverse cracking of asphalt pavements in the North-Eastern Poland <i>M. Pszczoła, J. Judycki & B. Dołżycki</i>	853
Evaluation of relationships between deflection-based indices and flexible pavement cracking field performance <i>S.W. Haider & K. Chatti</i>	861
 <i>13. Pavement cracking detection</i>	
Photogrammetric pavement detection system <i>T. Lovas, I. Kertész, I. Fi & A. Barsi</i>	873

Automated cracking survey <i>K.C.P. Wang, W. Gong & Z. Hou</i>	881
Crack detection and classification in asphalt pavement using image processing <i>A. Hassani & H. Ghasemzadeh Tehrani</i>	891
<i>14. Cracking control in concrete and bridge decks</i>	
Experimental and numerical simulation study on the crack of steel orthotropic bridge deck pavement <i>W. Xu & X.-N. Zhang</i>	899
Cracking of wearing courses on steel orthotropic bridge decks <i>X. Chen, W. Huang, J. Yang, X. Wang & G. Cheng</i>	907
Author Index	913

Preface

Pavement cracking is a major pavement distress, and its rehabilitation cost is astronomical. Because the mechanisms and the causes of cracking in concrete, flexible, and composite pavements are still not well understood, this RILEM Conference is both timely and necessary. The Conference addresses several issues including pavement crack initiation and propagation mechanisms, modeling, laboratory evaluation, field validation, and detection techniques.

The Conference is the sixth in a series of RILEM Conferences on cracking in pavements. The first four focused on reflective cracking while the fifth and sixth have a focus on pavement cracking. The following is a historical summary of the past conferences:

- RC1989 Liège: Pointed out the main factors and mechanisms involved in the initiation and propagation of cracks.
- RC1993 Liège: Focused on the theoretical and experimental research needed to optimize solutions.
- RC1996 Maastricht: Presented the importance of utilizing the appropriate interlayer systems and their applications. Introduced the benefits expected from modeling and the needs for structural design of overlays.
- RC2000 Ottawa: Shared the experiences of North America in reflective cracking.
- RC2004 Limoges: Shifted the focus to pavement cracking and advanced modeling; Established the RILEM technical committee on reflective cracking.

The 6th RILEM International Conference on Cracking in Pavements marks the first time the Conference is held in the United States. We are very pleased to host the Conference considering the growing interest in this topic in North America as was evidenced during RC2004 Limoges. The submitted papers were rigorously peer reviewed, and only 89 papers from 20 different countries were accepted for presentation and publication indicating the international nature of the Conference. The Conference Proceedings provide both a state-of-the-art and state-of-the practice record on modeling of cracking in pavements, experimental approaches, field investigations, case histories, and interlayer system effectiveness.

Due to the large number of papers, the Conference includes three parallel tracks. In addition, four events are taking place in conjunction with the Conference: a workshop on reflective cracking immediately prior to the Conference; an exhibition during the Conference, with several manufacturers and services related to pavement crack detection, rehabilitation, and material testing; a meeting of the RILEM Technical Committee on Reflective Cracking; and the mid-term meeting of the FHWA Expert Task Group on Fundamental Properties and Advanced Models.

Finally, we would like to acknowledge the Scientific and Organizing Committees for their continuing input and suggestions throughout the Conference planning and the many individuals who helped review the papers.

Imad L. Al-Qadi, Conference Chair
Tom Scarpas, Co-Chair
Andreas Loizos, Co-Chair
Chicago, June 2008

Organization

Chairmen

Imad Al-Qadi, Chairman
Tom Scarpas, Co-Chairman
Andreas Loizos, Co-Chairman

University of Illinois at Urbana-Champaign, USA
Delft University of Technology, The Netherlands
National Technical University of Athens, Greece

Scientific Committee

Chairman
Secretary

Imad Al-Qadi, USA
Leslie Elble, USA

Gordon Airey, UK
Hussain Al-Khalid, UK
Hussain Bahia, USA
Bill Buttlar, USA
Samuel Carpenter, USA
Armelle Chabot, France
Emmanuel Chailleux, France
Andrew Collop, UK
Mauro Coni, Italy
Morris de Beer, South Africa
Arian De Bondt, The Netherlands
Herve Di Benedetto, France
Guy Dore, Canada
Mostafa Elseifi, USA
Ali Farhang, Sweden
Edward Guo, USA
A. Abdel Halim, Canada
Will Hansen, USA
Gerry Huber, USA
Anastasios Ioannides, USA
Ilan Ishai, Israel
Elin Jensen, USA
Lev Khazanovich, USA
Richard Kim, USA
Niki Kringos, The Netherlands
Samer Lahouar, Tunisia

Xueyan Liu, The Netherlands
Bob Lytton, USA
Johan Maeck, Belgium
Mihai Marasteanu, USA
Mark Marienfeld, USA
Eyad Masad, USA
Ann Millien, France
Andre Molenaar, The Netherlands
Antonio Montepara, Italy
Jorge Pais, Portugal
Manfred Partl, Switzerland
Glaucio Paulino, USA
Daniel Perraton, Canada
Christophe Petit, France
Katherine Petros, USA
Annabelle Phelipot, France
Rob Rasmussen, USA
Jeff Roesler, USA
Reynaldo Roque, USA
Johan Silfwerbrand, Sweden
Jorge Soares, Brazil
Dariusz Sybilski, Poland
Gabriele Tebaldi, Italy
Erol Tutumluer, USA
Jacob Uzan, Israel
Tom Van Dam, USA
Julie Vandenbossche, USA

Organizing Committee

Imad Al-Qadi, USA
Jongeeun Baek, USA
William Buttlar, USA
Leslie Elble, USA
Eli Fini, USA
Zhen Leng, USA
Hasan Ozer, USA

Geoff Roberts, USA
Jeff Roesler, USA
Tom Scarpas, The Netherlands
Leslie Sweet Myrick, USA
Erol Tutumluer, USA
Hao Wang, USA

Reflective cracking behavior for traffic and temperature effects

M.J.C. Minhoto

Bragança Polytechnic Institute, Bragança, Portugal

J.C. Pais & P.A.A. Pereira

University of Minho, Guimarães, Portugal

ABSTRACT: This paper presents a study on the influence of the effects of temperature variations, in comparison with traffic effects, on the reflective cracking overlay behavior. It is intended to contribute to the improvement of the pavement overlay design methods which consider reflective cracking as one among distress criteria. The development of this study was based on the numerical simulation of the overlay behavior, through the implementation of numerical thermal and mechanical models based on the finite element, considering the simultaneous action of traffic and temperature variations and their influence on reflective cracking.

1 INTRODUCTION

The aim of the paper is to present a study on the influence of temperature variations on the reflective cracking overlay. With the obtained knowledge, emphasis will be placed on the improvement of the pavement overlay design methods, by demonstrating the possibility to develop relationships that consider temperature variation effects in relation to the reflective cracking phenomena in the pavement overlay design methodologies. The developments of this study were supported on the numerical simulation of the overlay behavior, based on the finite element methodology and considering the simultaneous loading of traffic and temperature variations on a conventional asphalt overlay.

This study also involves an evaluation of the hourly stresses and strains, generated by traffic and thermal loading characterized through temperature variation in the full-depth of the pavement during a year. That temperature distribution throughout the pavement structure was obtained by field measurements in a pavement section located along IP4 main road, near Bragança (northeast of Portugal), for a period of a year, using a temperature-recording equipment. Traffic data were obtained in field near the temperature measurements location.

The 3D finite element methodology was used to model the reflective cracking phenomena, in order to calculate the stresses and strains associated to each single case of loading: traffic (130 kN axle load) and observed full-depth pavement temperatures. Based on those strains results, the strain state of the combination of both cases was evaluated.

In the case of thermal loading strain evaluation, the bituminous material behavior was considered as viscoelastic, characterized by the relaxation modulus, as the overall state of tension in the overlay caused by the temperature variation is time-dependent and thus function of the viscoelastic response of the bituminous materials. In the case of traffic loading the bituminous material behavior was considered as “elastic” material, characterized by the stiffness modulus.

Those computed stresses and strains became concentrated above the existing cracks, creating an active zone of pavement overlay failure or crack propagation. The traffic and thermal stresses and strains, calculated for each case of loading, were used to verify the influence of the thermal loading in the overlay behavior through the evaluation of the hourly damage associated to each type of load.

The overlay damage evaluation was made hourly along the year was made through the ratio between the hourly observed traffic and the hourly predictive overlay life. The overlay life evaluation was made using the mechanistic-empirical methodology proposed by Sousa et al (2005).

This methodology is capable of assembling Modes I and II deflection patterns simultaneously on asphalt concrete specimens into a coherent procedure. The influence of pavement characteristics on state of stress and strain was considered by applying the Von Mises strain deviator, expressed by Equation 1.

$$\varepsilon_{VM} = \frac{1}{1+\nu} \sqrt{\frac{1}{2}((\varepsilon_1 - \varepsilon_2)^2 + (\varepsilon_1 - \varepsilon_3)^2 + (\varepsilon_2 - \varepsilon_3)^2)} \quad (1)$$

where ε_{VM} is the Von Mises strain and $\varepsilon_1, \varepsilon_2, \varepsilon_3$ are the principal strains.

This mechanistic-empirical methodology is based on the results of flexural fatigue tests, in controlled strain, based on the Von Mises strain as the “controller” parameter of the phenomenon. For beam fatigue test conditions subjected to four-point bending, ε_{VM} can also be written as:

$$\varepsilon_{VM} = \varepsilon_{fat} (1 + \nu) \quad (2)$$

where ε_{fat} is the fatigue strain for beam fatigue test conditions subjected to four-point bending.

2 THERMAL LOADING

The full-depth pavement structure temperature distribution was obtained through field measurements, using temperature-recording equipment – a Datalogger associated with thermocouples – because, by this means, actual temperature can be reliably measured. However, this method is relatively slow and it only provides information about temperature in the measurement period (Minhoto et al, 2005). During twelve months (January 2004 to December 2004) pavement temperatures were measured at a new pavement section, located at IP4 main road, near Bragança (north of Portugal). At that location, seven thermocouples were installed in the pavement at seven different depths: at surface, 0.028 m, 0.055 m, 0.125 m, 0.165 m 0.220 m and 0.340 m.

The depths were chosen to offer a proper representation of the whole asphalt concrete layers (0.340 m). The temperatures were recorded at every hour, every day, allowing to produce the visualization of the annual temperature evolution, such as the observed temperatures at the bottom of the overlay, as presented in Figure 1. In that figure the typical temperature variations of summer and winter periods are clearly identified.

3 PAVEMENT MODELLING

The pavement structure was modeled as presented in Figure 2. For crack reflection analysis the top layer represents the bituminous overlay and the subjacent layer represents the old cracked bituminous layer, where a crack is modeled by elements without stiffness.

The finite element model used in three-dimensional numerical analysis was developed by using a general finite elements code, ANSYS 7.0. The design of a mechanical model is based on a finite element mesh definition, oriented to mechanical analysis, considering a finer element mesh closer to the pavement surface, nearer the wheel load point and in the overlay above the crack. An eight-node structural solid element was used assuming linear approximation of the displacement field and three degrees of freedom per node.

The model is 4.63 m long, 7.45 m wide and 2.24 m thick. The model total thickness is the result of all pavement layers thicknesses: 0.125 m overlay, 0.215 m cracked layer, 0.30 m aggregate base layer and 1.6 m subgrade. A longitudinal crack was modeled on the layer which is just below the

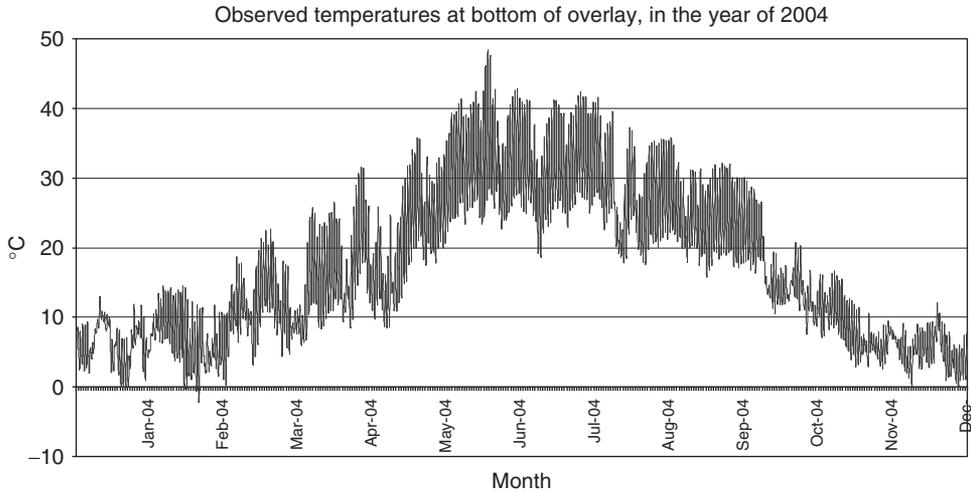


Figure 1. Observed temperatures at overlay bottom.

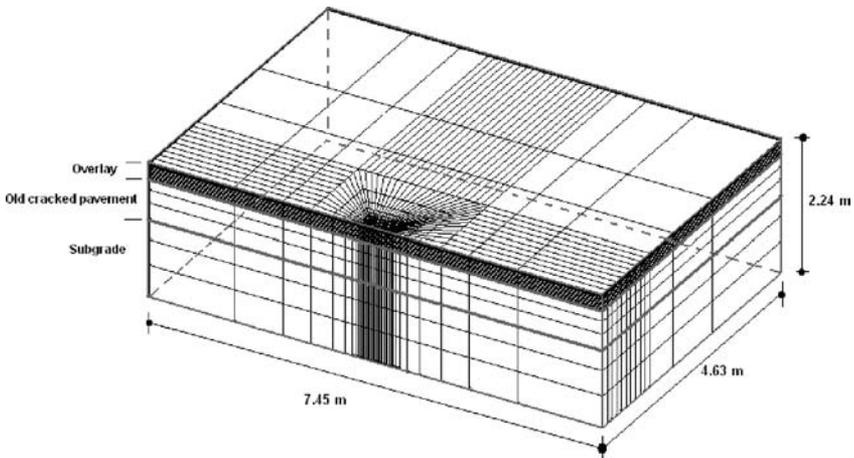


Figure 2. Structural model configuration used in numerical simulation.

overlay with 10 mm width. The resulting number of elements was 13538, in both traffic and thermal cases.

The first effort in order to verify and calibrate the purely FEM mechanical analysis of a cracked pavement before and after the overlay was accomplished by comparing the vertical crack activity measured in the model with the one measured in the pavement using a crack activity meter, according to the model developed by Pais et al (2002). The calibration was accomplished by comparing the crack movements in a pavement and in the FEM model for two different conditions: before and after the pavement overlay.

Once the type of processing depends on the loading case considered, for thermal loading, the model processing was carried out as a transient process (time-rate dependent), because that load type is a long term load, and the material properties are time-rate dependent. For the traffic loading case, the model processing was based on a steady-state process, as that load is considered to be a short-term load, and the material properties were defined as elastic material, or non-time-dependent.

Table 1. Elastic properties of the bituminous mixture used in this study.

Temperature (°C)	Stiffness (MPa)
-5	16157
5	13563
15	9304
25	478

4 MECHANICAL PROPERTIES

The stiffness modulus for modeling was obtained from flexural fatigue tests, conducted according to the AASHTO TP 8-94, performed for 4 different temperatures: -5°C ; 5°C , 15°C and 25°C . The stiffness modulus values obtained for the conventional mix used in this work are presented in Table 1.

The fatigue behavior considered for the studied mixtures was evaluated after the stiffness modulus tests for the same test temperatures. For each test temperature (-5°C ; 5°C , 15°C and 25°C) a fatigue life law was achieved and fitted in the following model:

$$N_f = \left(\frac{\varepsilon_t}{(aV_b + b)E^{-c}} \right)^{-d} \quad (3)$$

where N_f is the fatigue resistance, ε_t is the strain level, E is the stiffness modulus, V_b is the volume of the binder in the mixture, $a = 1.009$; $b = 0.9283$, $c = -0.3772$ and $d = 3.961$

For the temperature variation modeling, it was considered that the bituminous material shows a linear viscoelastic behavior, time-and-temperature dependent, modeled through thermal-reological simplicity principle. With this principle, the relaxation curve for high temperatures is identical to the low temperature relaxation curve, when loading time is scaled.

Relaxation tests were also performed at -5°C , 5°C , 15°C and 25°C , using bituminous samples of the conventional mix. Tests results were fitted in kernel functions and considering the thermal-reological simplicity principle, elastic shear modulus, G_i , elastic volumetric modulus, K_i , relaxation modulus, τ_i , and C_1 and C_2 for WLF function were obtained and presented in Table 2.

Thermal contraction tests were performed and the coefficient of thermal contraction, constant and independent from temperature, obtained for this study was $3.54 \times 10^{-5}/^{\circ}\text{C}$. The Poisson's ratio was assumed to be constant and the value adopted was 0.35 for bituminous layers and subgrade and 0.30 for granular layers.

5 SIMULATION PROCEDURES

The simulation procedures to achieve the purposes of this study involved a multiple 3-D finite-element runs considering the pavement structure referred above. Each solution was obtained for each hour and for each loading case (traffic, temperature variation and both superimposed). The main analysis procedure involved in the present study is schematized in Figure 3.

In the first stage, for each hour of the day along a year, all nodal pavement temperatures of the finite element model were calculated by using the thermal model, a steady-state thermal analysis based, and applied in all nodes of traffic and temperature variation models. The input data of the thermal model were the field pavement temperatures obtained in the seven points of the pavement.

Table 2. Prony parameters of the bituminous mixture used in this study.

Parameters	Value
Shear Parameters	
K_∞	2.81E + 01
K_1	7.85E + 02
K_2	2.60E + 02
K_3	3.07E + 01
τ_1^K	5.85E - 01
τ_2^K	9.16E + 00
τ_3^K	9.92E + 03
Volumetric Parameters	
G_∞	1.04E + 01
G_1	2.89E + 02
G_2	9.45E + 01
G_3	1.13E + 01
τ_1^G	5.99E - 01
τ_2^G	9.49E + 00
τ_3^G	1.00E + 04
WLF	
T_r	1.31E + 01
C_1	2.56E + 07
C_2	1.39E + 08

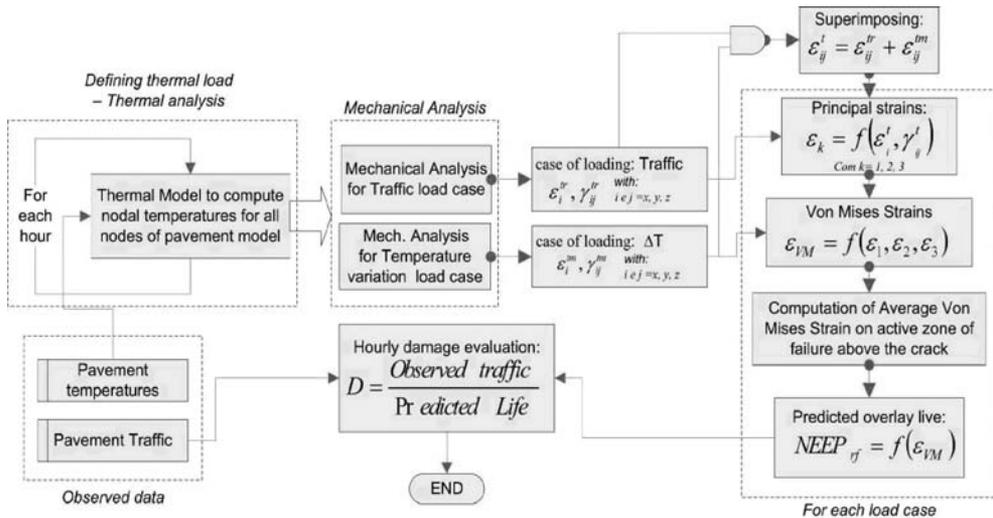


Figure 3. Procedures involved in the study.

The computed pavement temperatures were applied in all nodes of the traffic model to set the elements stiffness for stress and strain calculation for 130 kN traffic loading case. The computed pavement temperatures were also applied in all nodes of thermal mechanical model.

The strain and stress states obtained for traffic loading and temperature variations were superimposed to obtain the stress and strain states for resulted loading. After that, the average Von Mises strains in the finite element nodes above the crack zone were computed for each case. This Von Mises strains were used to estimate the overlay life of each studied case.

Equation 2 was used to relate the average Von Mises strain with a fatigue strain concept used on flexural fatigue laws, obtained from four-point flexural fatigue tests, normally used to evaluate the prediction of pavement life. In this way, fatigue life was estimated considering the Von Mises strain of the overlay. The four-point flexural fatigue tests performed to obtain the fatigue laws to be used in this study were carried out at different temperatures. Those fatigue laws were developed in terms of temperature-dependency.

The overlay life was obtained from nodal temperature occurred in the zone above the crack at every hour. After that, the hourly damage was evaluated.

6 VON MISES STRAIN AND OVERLAY LIFE RESULTS

In one-year time-period the main results obtained from this simulation were: i) the Von Mises strains; ii) predicted overlay life; iii) overlay damage. These calculations were performed for traffic loading, temperature variations and the combination of both, traffic and temperature. In Figure 4, the hourly means Von Mises strain evolution along the year is plotted against the time.

The Von Mises strain for each loading case was used to predict the pavement life after overlying. Figure 5 shows the hourly predictive overlay life resulting from traffic and traffic + ΔT loading cases.

The results show that the overlay life obtained from traffic loading is higher than the overlay life obtained from traffic + ΔT loading, mainly in winter season, when low temperatures occur. In summer, the predicted overlay life is inferior to that of winter. Thus, the effect of traffic + ΔT may have a significant influence on the overlay life, which will justify a special attention.

7 DAMAGE RESULTS

Knowing the predicted overlay life and the number of axles distribution during the year allows to perform an annual damage evolution estimation. The damage evaluation is made in terms of damage distribution and in terms of accumulated damage evolution, measured hourly and monthly.

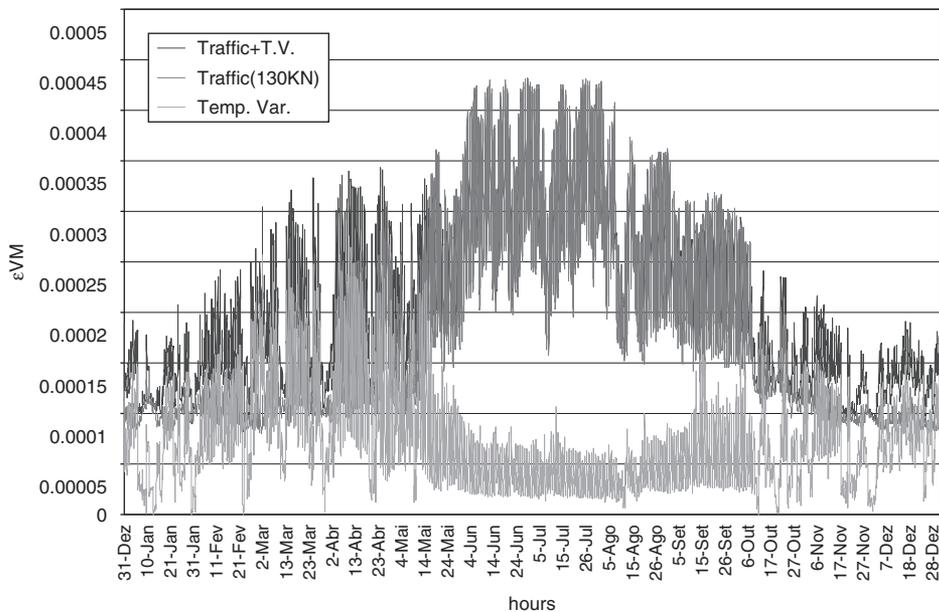


Figure 4. Von Mises strain for all loading cases.

Figure 6 shows the accumulated monthly damage occurred in a conventional mix overlay for traffic and traffic + ΔT . In this figure the accumulated monthly damage occurred in relation to traffic loading is lower than the damage observed for traffic + ΔT . Thus, the traffic + ΔT effect in the overlay damage may have a significant influence when compared with traffic effects that should be considered in a design process..

Monthly and annual damage for the real loading conditions (traffic and temperature variations) was obtained from the previously presented results, as shown in Table 3.

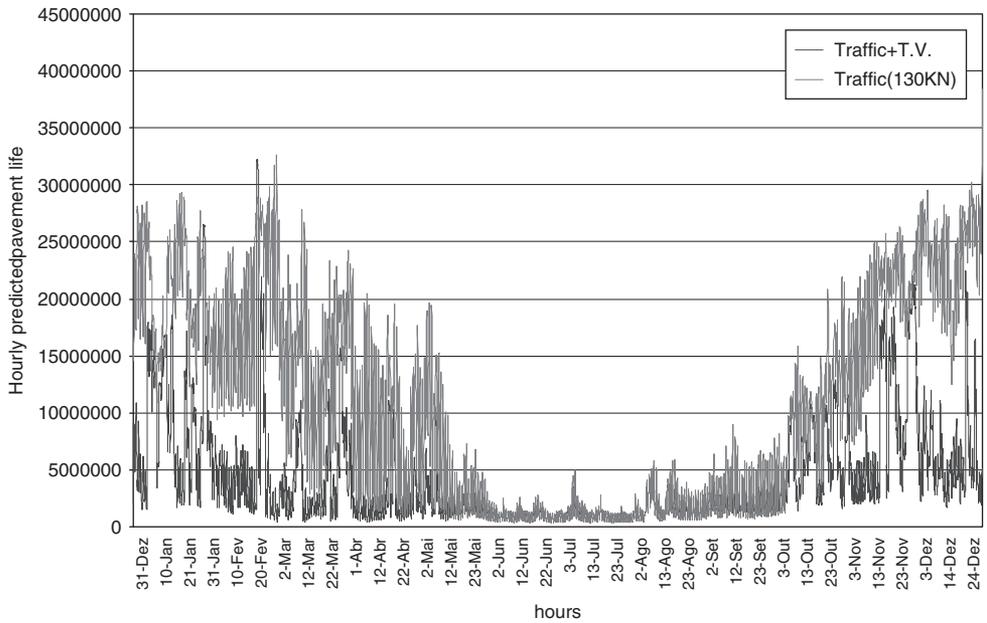


Figure 5. Predicted overlay life for traffic + temperature variations.

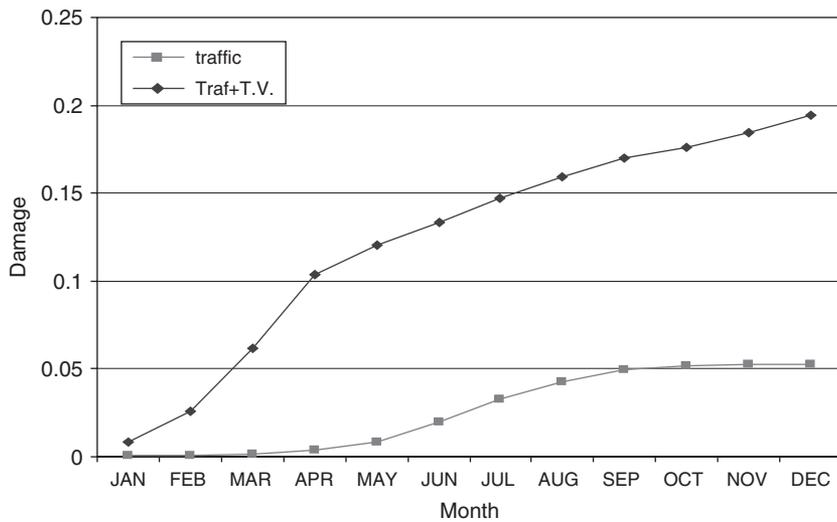


Figure 6. Accumulated monthly damage occurred in a conventional mix overlay.

Table 3. Real monthly and annually damage for real loading conditions.

Period	Air temperature				Real damage
	T_{ref}	ΔT	T_{min}	T_{mean}	
January-04	10.14	8.06	2.08	5.96	0.008340
February-04	11.02	10.67	0.36	5.06	0.017382
March-04	11.69	9.95	1.73	6.65	0.036154
April-04	15.69	13.13	2.56	9.41	0.041459
May-04	19.68	12.29	7.39	13.68	0.017202
June-04	28.13	15.22	12.91	20.99	0.012995
July-04	27.68	15.17	12.51	20.58	0.013910
August-04	25.78	11.49	14.29	20.30	0.011692
September-04	25.16	16.46	8.70	16.62	0.010663
October-04	16.75	9.12	7.63	11.98	0.006598
November-04	10.09	9.13	0.97	4.95	0.008147
December-04	9.08	9.45	-0.37	3.81	0.010155
Annual	20.80	13.15	7.65	14.27	0.194697

8 THEORETICAL SIMULATION

The reflective cracking evaluation presented needs time investment in terms of computing processes and does not provide immediate results. Thus, the development of procedures that allow a rapid evaluation of the damage associated to each loading condition is important for this study, mainly for the development or improvement of the pavement overlay design methodologies in order to consider the temperature variations effect in the reflective cracking phenomena.

Thus, the development of relationships between the thermal loading parameters and the corresponding pavement damage and the development of shift factors between that theoretical damage and the damage for real loading conditions are some of the purposes of the present research.

For a large number of “theoretical standard situations” of temperature variations loading, the hourly damage was calculated in order to establish a direct relationship between those two variables (loading conditions and associated damage). The standard situations of temperature variations are characterized, for a period of twenty four hours, by means of two parameters: reference temperature, T_{ref} (the maximum daily air temperature), and the maximum daily temperature variation, ΔT . Those situations were considered theoretical and it was assumed that these conditions happened during the analysis period. The theoretical damage was calculated for the observed traffic.

First, for each theoretical loading situation, an hourly distribution was adopted, for twenty-four hours, for the main atmospheric parameters that influence the pavement thermal state, specifically the air temperature evolution, the solar radiation evolution, the mean wind speed and the full-depth pavement temperature distribution for the initial thermal state. Those parameters were established through an exhaustive analysis of temperature measurements.

After that, the evaluation of the theoretical stress/strain states in the pavement overlay associated to each standard situation was carried out. This procedure involved the use of simulation thermal models for full-depth pavement temperature determination. Considering these temperatures, mechanical models were applied to determinate the stress/strain states in the pavement overlay.

A set of damage curves between (T_{ref} , ΔT) and the obtained damage were deduced. Each damage curve represents the variation of the damage during any period, as a function of the temperature variation, ΔT , for a specific reference temperature, T_{ref} . Figure 7 presents the curves of the annual damage for a reference temperature, T_{ref} , respectively.

The establishment of a reasonable number of damage curves allowed developing a statistical study for fitting the results within a generalized law. These results provide evidence that monthly

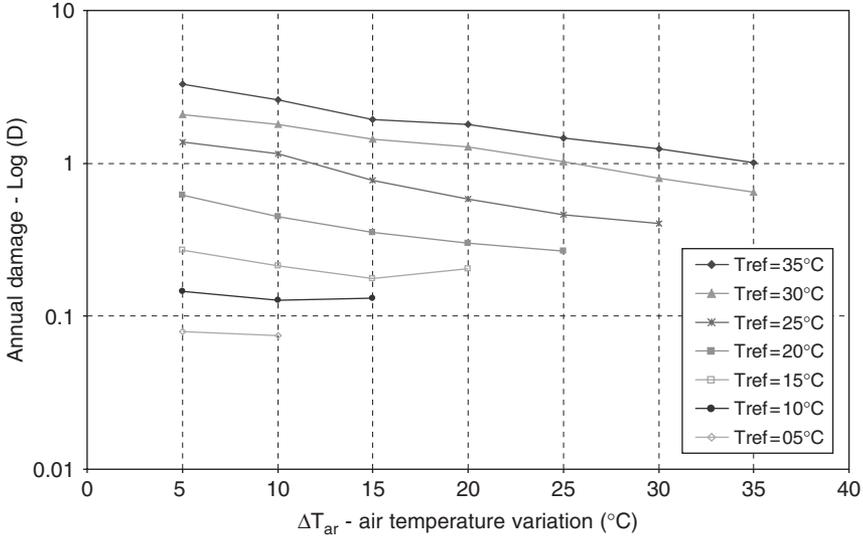


Figure 7. Overlay damage for theoretical simulations.

Table 4. Generalized constant values for monthly damage evaluation.

Validation range	Constant values			R ²
	a	b	c	
35°C < T _{ref} < 15°C	1.770E - 06	2.617E + 00	-5.653E - 02	8.618E - 01
15°C < T _{ref} < 5°C	8.388E - 04	1.199E + 00	-1.598E - 02	7.814E - 01

damage variation against reference temperature, T_{ref}, and temperature variations, ΔT, for each month, show an exponential trend, and the best-fit relationship obtained follows Equation 4.

$$damage = a \times T_{ref}^b \times e^{c \times \Delta T} \quad (4)$$

where: a, b and c = monthly damage fitting constants, for each month; T_{ref} = reference temperature; ΔT = temperature variation.

The a, b and c generalized constants were obtained statistically for each month, through the monthly damage evolution analysis, by fitting Equation 4 to damage values associated to the (T_{ref}, ΔT) standard cases. The constants obtained for the statistical analysis are presented in Table 4 and are function of the reference temperature.

With the real and theoretical damage values, obtained for each considered period, a representative factor between the theoretical damage and the real damage can be established for each standard situation. This factor, called “damage shift factor”, is expressed by Equation 4.

$$r = \frac{D_{monthly}^{real}}{D_{monthly}^{theoretical}} \quad (5)$$

where r = damage shift factor between theoretical and real damage; D_{real} = total monthly damage resulting from real traffic and temperature variations; D_{theoretical} = total monthly damage resulting from theoretical situations of traffic and temperature variations.

Table 5. Real damage, theoretical damage and damage shift factor.

Period	Air temperature				Real damage	Theoretical damage	Shift factor (Dr/Dt)
	T _{ref}	ΔT	T _{min}	T _{mean}			
January-04	10.14	8.06	2.08	5.96	0.008340	0.011862	0.703097
February-04	11.02	10.67	0.36	5.06	0.017382	0.012580	1.381666
March-04	11.69	9.95	1.73	6.65	0.036154	0.013649	2.648738
April-04	15.69	13.13	2.56	9.41	0.041459	0.018468	2.244931
May-04	19.68	12.29	7.39	13.68	0.017202	0.002151	7.995755
June-04	28.13	15.22	12.91	20.99	0.012995	0.004643	2.798691
July-04	27.68	15.17	12.51	20.58	0.013910	0.004463	3.116920
August-04	25.78	11.49	14.29	20.30	0.011692	0.004562	2.563000
September-04	25.16	16.46	8.70	16.62	0.010663	0.003232	3.298987
October-04	16.75	9.12	7.63	11.98	0.006598	0.001688	3.907951
November-04	10.09	9.13	0.97	4.95	0.008147	0.011599	0.702369
December-04	9.08	9.45	-0.37	3.81	0.010155	0.010169	0.998642
Annual	20.80	13.15	7.65	14.27	0.194697	0.524624	0.371117

Table 5 shows the “damage shift factor” values for each analysis period. The fitting statistical study for obtaining *a*, *b* and *c* constants was carried out monthly and during the global analysis period.

The analysis of Table 5 allows concluding that, during cold months, the values of the damage shift factor are values near 1. During warm months that parameter presents dispersion and, in the majority of cases, shows values higher than 1.

9 DESIGN PROCEDURES

The purpose of the present study is to develop a generalized overlay design methodology. It three phases: a) data definition; b) daily damage evaluation and c) performance evaluation.

Data definition and damage evaluation phases must have the same treatment as the procedure for the establishment of damage relationships previously presented.

In the future the proposed methodology must develop the process of evaluation of the hourly damage for 24 hours, which will consist in the application of relationships that produce the results obtained for traffic and thermal effects observed during the year. The establishment of relationships to obtain these objectives will have to observe the following aspects:

- the relationships for standard (theoretical) loading situations must be established with basis on the acceptance of two values of air temperature (T_{ref}, ΔT) as adopted in the second part of this paper.
- the relationships will have to be developed for several overlay structure types, characterized for diverse thicknesses of the pavement and several values of the stiffness of the existing layers, including that of the subgrade foundation.

The process of development of the relationship proposed must generally follow the procedures adopted in this paper. The resulting relationships will have to allow:

- the establishment of a pair of values (T_{ref}, ΔT) which must guarantee the calculation of a daily profile of Von Mises strains associated to the combination of traffic and variations of temperature loading;
- the establishment of a pair of values (T_{ref}, ΔT) which must allow the calculation of a daily profile that makes possible to obtain a permissible hourly traffic, as an alternative to the profile considered in the previous point;

- the establishment of a pair of values (T_{ref} , ΔT) which must guarantee the calculation of a daily profile of hourly damages associated to the combination of traffic loading and temperature variation.

10 CONCLUSIONS

The finite-element analysis was used to simulate the reflective cracking performance of bituminous mixture overlays throughout a year, considering the temperature variations as the main cause for reflective cracking. A thermal response of the pavement structure, made by a thermal analysis, was performed before a mechanical analysis. In the mechanical analysis the transient effect of relaxation was considered, once the overall state of tension in the overlay caused by the temperature variation is also a function of the viscoelastic response of the bituminous materials.

Temperature variations in bituminous layers (overlay and cracked layers) which cause a state of tension in the overlay are particularly important for estimating the overlay life. The effect of accumulated restrained thermal stresses, as a result of the effect of temperature variations shrinkage, added to the traffic loading effect, will reduce the overlay life. Thus, the effect of temperature variation will support the need for a special attention towards overlay design procedures.

This study has demonstrated that it is possible to include the effects of temperature variations in a design process of pavement overlays. For that, it is necessary to develop a methodology that includes relationships, such as the ones presented in this paper, for evaluating damage and shift factors to adjust the results to the real behavior of overlays.

REFERENCES

- Sousa, J.B., Pais, J.C., Saim, R., Way, G. & Stubstad, R.N. 2002. Development of a Mechanistic-Empirical Based Overlay Design Method for Reflective Cracking, Journal of the Transportation Research Board.
- Minhoto, M.J.C., Pais, J.C., Pereira, P.A.A. & Picado-Santos, L.G. 2005. "Predicting Asphalt Pavement Temperature with a Three-Dimensional Finite Element Model". Transportation Research Record: Journal of the Transportation Research Board n° 1919 – Rigid and Flexible Pavement Design 2005. pp. 96–110. TRB. Washington DC.
- Pais, J.C., Pereira, P.A.A., Sousa, J.B. & Capitão, S. 2002. "Evaluation of the load associated cracking in flexible pavements", Sixth International Conference on the Bearing Capacity of Roads, Railways and Airfields, Lisboa, Portugal, pp. 585–594.

Author Index

- Abd El Halim, A.O. 357
Akkaya, Y. 179
Akram, T. 529
Al-Qadi, I.L. 563, 661, 801
Allen, D.H. 295, 599
Ammendola, R. 539
Antunes, M.L. 791
Arnaud, L. 261
Artamendi, I. 417
- Baek, C. 315
Baek, J. 563, 801
Bahia, H.U. 469
Bai, B.-Q. 617
Baladi, G.Y. 529
Balay, J.M. 13, 55, 671
Barsi, A. 873
Baumgardner, G. 843
Bažant, Z.P. 137
Bennert, T. 833
Birgisson, B. 811
Bodin, D. 13
Bouhas, F. 609
Braham, A.F. 369
Brake, N.A. 155
Breitenbücher, R. 127
Bressette, T. 45
Buonsanti, M. 587
Buttler, W.G. 369, 683, 801
- Cebon, D. 627
Chabot, A. 13, 55, 671
Chaignon, F. 721
Chatti, K. 155, 861
Chaverot, P. 457
Chehab, G.R. 769
Chehab, G.R. 721
Chen, X. 907
Cheng, G. 907
Ciampa, D. 201
Clyne, T. 405
Collop, A. 395
Cominoli, L. 89
Coni, M. 271
- Cooley, L.A. 843
- Dai, P. 229
Daranga, C. 469
Dave, E.V. 369
Davis, L. 703
de Bondt, A.H. 437
de Freitas, F.A.C. 295
de Larrard, F. 671
Delaporte, B. 457
Deloffre, L. 13
Dendurant, J. 703
Di Benedetto, H. 283, 457
Diakhaté, M. 649
Dołżycki, B. 853
Dong, Z.-J. 387
Doré, G. 447
- Easa, S. 357
El-Desouky, A. 357
Feng, Z. 575
Ferron, R.P. 179
Fi, I. 873
Fontul, S. 791
Fratta, D. 469
- Gauthier, G. 457
Ghasemzadeh Tehrani, H. 891
Gibson, N. 35, 405
Gibson, N.H. 305
Goacolou, H. 649
Gong, W. 881
Gong, W.-Q. 387
Guddati, M.N. 315, 575
Guissi, G. 447
Guo, E.H. 25
- Haider, S.W. 155, 529, 861
Hajj, E.Y. 821
Hansen, W. 119
Harvey, J. 741
Harvey, J.T. 3, 45
Hassani, A. 891
Himeno, K. 509
- Hook, K.D. 713
Hoover, C.G. 137
Hornych, P. 13
Hou, Z. 881
Houel, A. 261
Howard, I.L. 843
Hu, S. 333, 637
Hu, X. 333, 345, 637
Huang, W. 907
Huang, X.-M. 327
Hussain, A. 529
- Isola, R. 271
Jia, L. 345
Jones, D. 45, 741
Judycki, J. 853
- Kabir, M.D. 427
Kannekanti, V. 69
Kertész, I. 873
Kerzreho, J.P. 13
Khalid, H.A. 417
Khedoe, R.N. 481
Kim, S. 769
Kim, Y.-R. 295, 599
Kim, Y.R. 315, 575
Kogo, K. 509
Kohler, E. 69
Kutay, M.E. 305
Kwon, S.H. 179
- la Agostinacchio, M. 201
Labuz, J.F. 501
Lee, K. 315
Leng, Z. 661
Leonardi, G. 587
Li, Q. 211
Li, Q.-F. 327
Li, X. 501
Little, D.N. 575
Loizos, A. 519
Losa, M. 239
Lovas, T. 873
Lu, H. 221
Lüddecke, F. 779

Maeck, J. 491, 761
 Maher, A. 833
 Marasteanu, M. 405, 469
 Marasteanu, M.O. 501
 McDowell, G. 395
 Meda, A. 89
 Millien, A. 55, 609, 649
 Minhoto, M.J.C. 551
 Mohammad, L.N. 427
 Molenaar, A.A.A. 189, 251, 481
 Montepara, A. 811
 Morian, N.E. 821
 Moro, A. 539
 Mostafa, A. 357
 Nantung, T. 109
 Newbolds, S.A. 167
 Nguyen, M.L. 283
 Ni, F.-J. 211

 Ojo, J.O. 469
 Olek, J. 167
 Olita, S. 201
 Oliveira, J.R.M. 271
 Ozer, H. 661

 Pais, J.C. 551
 Palacios, C. 721
 Papavasiliou, V. 519
 Paulino, G.H. 369, 683
 Penman, J. 713
 Pereira, P.A.A. 551
 Perraton, D. 447
 Petch, F. 25
 Petit, C. 609
 Petit, Ch. 55, 649
 Phelipot-Mardelé, A. 649
 Pierre, P. 447
 Pinelo, A.M. 791
 Pirkawetz, S. 779
 Plizzari, G.A. 89

 Portas, S. 271
 Portillo, O. 627
 Pouteau, B. 649, 671
 Powell, R.B. 731
 Praticò, F.G. 239, 539
 Pszczoła, M. 853
 Pu, B. 189
 Pérez, S.A. 55

 Qi, X. 35

 Raoufi, K. 109
 Recknagel, C. 779
 Ricalde, L. 25
 Roesler, J.R. 79
 Romeo, E. 811
 Roncella, R. 811
 Roque, R. 811
 Ross, M. 843

 Saadeh, S. 427
 Salama, H. 155
 Sauzeat, C. 283
 Schlangen, E. 119
 Scopelliti, F. 587
 Sebaaly, P.E. 821
 Shah, S.P. 179
 Shitangkoon, W. 695
 Sievering, C. 127
 Soares, R.F. 599
 Subramanian, V. 315
 Sun, L. 333, 345

 Tamagny, P. 55
 Tan, Y.-Q. 387
 Tang, X. 769
 Tayabji, S.D. 145
 Tebaldi, G. 811
 Thompson, M. 721
 Tsai, B.-W. 741
 Turos, M. 405
 Tyson, S.S. 145

 Ullidtz, P. 741
 Underwood, B.S. 315

 Van Rompu, J. 457
 van Rooijen, R.C. 437
 Vanelstraete, A. 491, 761
 Velásquez, R. 405
 Vervaecke, F. 491, 761
 v.d. Ven, M.F.C. 481
 Vázquez, J.R. 99

 Walubita, L.F. 333
 Wang, D. 79
 Wang, K.C.P. 881
 Wang, P. 327
 Wang, X. 907
 Wei, Y. 119
 Weiss, J. 109
 Wen, H. 695
 Wendling, L. 55, 283
 Wu, J. 395
 Wu, R.Z. 3

 Xu, H.-N. 387
 Xu, W. 899

 Yang, J. 221, 229, 907
 Yang, Y. 221, 229
 Yang, Z.-T. 327
 Yin, H.M. 683
 Youtcheff, J. 35, 305
 Yu, B. 229
 Yu, H.T. 145

 Zeghal, M. 379
 Zhang, P. 575
 Zhang, X.-N. 899
 Zhou, F. 637
 Zieliński, P. 751
 Zofka, A. 369

Internationally, much attention is given to causes, prevention, and rehabilitation of cracking in concrete, flexible, and composite pavements. The Sixth RILEM International Conference on Cracking in Pavements (Chicago, June 16-18, 2008) provided a forum for discussion of recent developments and research results. This book is a collection of papers from the Conference, and includes contributions on a variety of topics:

- Modeling of the initiation and propagation of pavement cracking
- Top-down and bottom-up fatigue cracking mechanisms
- Laboratory testing techniques and evaluation effectiveness
- Construction approaches and their relation to crack development
- Crack surveys and nondestructive evaluation
- In-situ experimental studies: field construction and rehabilitation techniques to inhibit pavement cracking
- Performance of crack preventative techniques and pavement service life prediction
- Interlay system effectiveness
- Pavement cracking evaluation using accelerated pavement testing
- Hot-mix asphalt overlay characterization
- Pavement interface modeling and testing
- Laboratory and field model validation
- Low-temperature cracking mechanisms and field studies
- Cracking in semi-rigid and stabilized pavement layers
- Analytical and experimental investigations of concrete joints
- White topping performance

Pavement Cracking: Mechanisms, Modeling, Detection, Testing, and Case Histories is particularly of interest to academics, researchers, and practitioners involved in pavement mechanics and performance.



CRC Press
Taylor & Francis Group
an informa business
www.crcpress.com

6000 Broken Sound Parkway, NW
Suite 300, Boca Raton, FL 33487
270 Madison Avenue
New York, NY 10016
2 Park Square, Milton Park
Abingdon, Oxon OX14 4RN, UK



an **informa** business